

## Method for Obtaining Zinc Absorber From Local Raw Materials

Tavashov Shakhzod Khujakhmatovich

Associate professor of the Karshi State Technical University

### Annotation

The results of studies on the preparation of the used catalyst GIAP-10 absorber are presented. Decomposition at a rate of 120% nitric acid 30%, temperature 95°C, leaching time 3 hours, before precipitation of zinc hydroxide carbonate from the resulting zinc nitrate solution with a precipitant solution with ammonium carbonate at pH medium (8.0-10.0), temperature 65 -70°C and the time is 1 hour. The obtained zinc hydroxide carbonate was dried at a temperature of 120°C, 2 hours and calcined at 500°C, 5 hours until it was converted to zinc oxide. Preparation of a scavenger based on zinc oxide in the form of a granule with the use of various binder and additives and amounts. Studied the effect of different amounts of binding additives on physical and chemical parameters. With an increase in the amount of binding additives CuO from 5% to 10% and MgO 7%, the degree of increase in the bulk density from 0.95 g/cm<sup>3</sup> to 1.02 g/cm<sup>3</sup>, the mechanical strength: the index of splitting strength increases from 0.37 kg/mm to 0.41 kg/mm and specific surface area from 93.1 m<sup>2</sup>/g to 97.8 m<sup>2</sup>/g.

**Keywords:** preparation, catalyst GIAP-10, absorber, nitric acid, zinc nitrate, temperature, an hour, pH, zinc hydroxide carbonate, zinc oxide, the bulk density, the mechanical strength, specific surface area.



This is an open-access article under the [CC-BY 4.0](https://creativecommons.org/licenses/by/4.0/) license

Natural gas is purified from sulfur compounds by absorption, followed by removal of H<sub>2</sub>S from the regeneration gases to obtain sulfur by the Claus method and fine purification on zinc oxide absorbers [1].

Zinc oxide absorbers are designed for fine purification of natural gas from sulfur compounds. Used absorbers are replaced with fresh ones after saturation with sulfur. One-time loading of desulfurization devices in the chemical industry will require hundreds of tons of zinc oxide absorbers. Absorbers discharged from the apparatus are production waste. More than 1000 tons of waste absorber have been accumulated at domestic enterprises of the chemical industry [2].

The article presents the results of studies to the effect of different amounts of binding additives on physical and chemical parameters The study of literature survey is presented in section III, methodology is explained in section IV, section V covers the experimental results of the study, and section VI discusses the future study and conclusion.

Previously studied samples of absorbers of sulfur compounds obtained in laboratory conditions from spent absorbers, the content of the mass fraction of zinc oxide is 89.8% and 88.1%, magnesium oxide is 7.4% and 6.8%, respectively, from absorbers from JSC “Maksam- Chirchik” and with JSC “Fergana-Azot”, at a rate of 85.0% ZnO and 5-8% MgO. The bulk density in the samples is 0.98 g/dm<sup>3</sup> and 0.83 g/dm<sup>3</sup> at a rate of (1.1÷1.4) g/dm<sup>3</sup>. Splitting strength index is equal to 0.71 kg/mm and 0.46 kg/mm with a norm of not more than 0.7 kg/mm and not less than 0.35 kg/mm. The specific surface area in the obtained samples of absorbers of sulfur compounds is 64.0 m<sup>2</sup>/g and 64.6 m<sup>2</sup>/g at a rate of at least 20.0 m<sup>2</sup>/g, respectively, for absorbers from JSC “Maksam-Chirchik” and JSC Ferganaazot, which meets the requirements of KSt 6.3-97: 2005 [4].

In the studies applied methods of the preparation of the absorber in laboratory conditions was molded on a manual syringe press based on zinc oxide in the form of granules (cylindrical) with the use of various binders and additives and the amount was mixed for 30 minutes. Before the formed mass has elastic-plastic-viscous properties. The molding mass is prepared from ZnO (act) sifted through a sieve with aperture size of 1 mm. Strengthening additives were used CuO, MgO, Al<sub>2</sub>O<sub>3</sub>, high-alumina cement, etc. to obtain absorbers in the form of granules. Drying was carried out in a muffle furnace at a temperature of 120°C for 3 hours.


We studied the effect of different amounts of binding additives on the physicochemical parameters of the absorbers of sulfur compounds (bulk density, mechanical strength and specific surface area) of the obtained absorbent.

The table shows the results of studies of the effect of binding additives on the degree of increase in physicochemical and mechanical indicators (bulk density, mechanical strength and specific surface area) of absorbers of sulfur compounds based on zinc oxide with the addition of various amounts of binding additives.

**Table. Effect of different amounts of binding additives on the physicochemical parameters of the absorber**


№	The name of indicators	Synthesized absorber sample						
		№1	№2	№3	№4	№5	№6	№7
1	Mass fraction of ZnO, %	95	93	90	85	88	86	83
2	Mass fraction of CuO, %	-	-	7	10	5	7	10
3	Mass fraction of MgO, %	5	7	3	5	7	7	7
4	Dimensions outer diameter of granules, mm	6,2	6,2	6,2	6,3	6,2	6,1	6,2
5	Bulk density, g/cm <sup>3</sup>	1,01	1,04	1,17	1,25	0,95	0,99	1,02
6	Mechanical strength: splitting strength index, kg/mm, granule diameter not less average-0.7 minimum -0.35	0,34	0,37	0,35	0,38	0,37	0,39	0,41
7	Specific surface, m <sup>2</sup> /g	75,2	78,7	80,3	85,7	93,1	95,3	97,8

Further, the influence of the amount of binding additives CuO and MgO on the degree of increase in the physicochemical and mechanical parameters (mechanical strength and specific surface) of the absorber of sulfur compounds was investigated when adding an additive of CuO from 5% to 10% and MgO 7%. The results are shown in Figures 1 and 2.

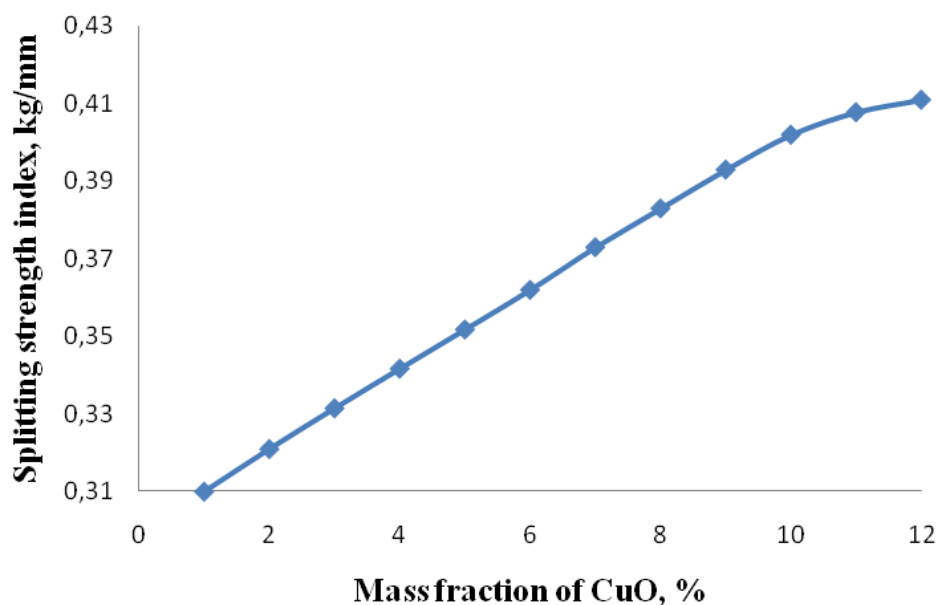

**Figure 1. Influence of CuO on the degree of increasing the splitting strength index**

Increase in the amount of CuO from 5% to 10% and MgO 7% on the degree of increase in mechanical strength: splitting strength of absorbers of sulfur compounds based on ZnO from 0.37 kg/mm to 0.41 kg/mm.

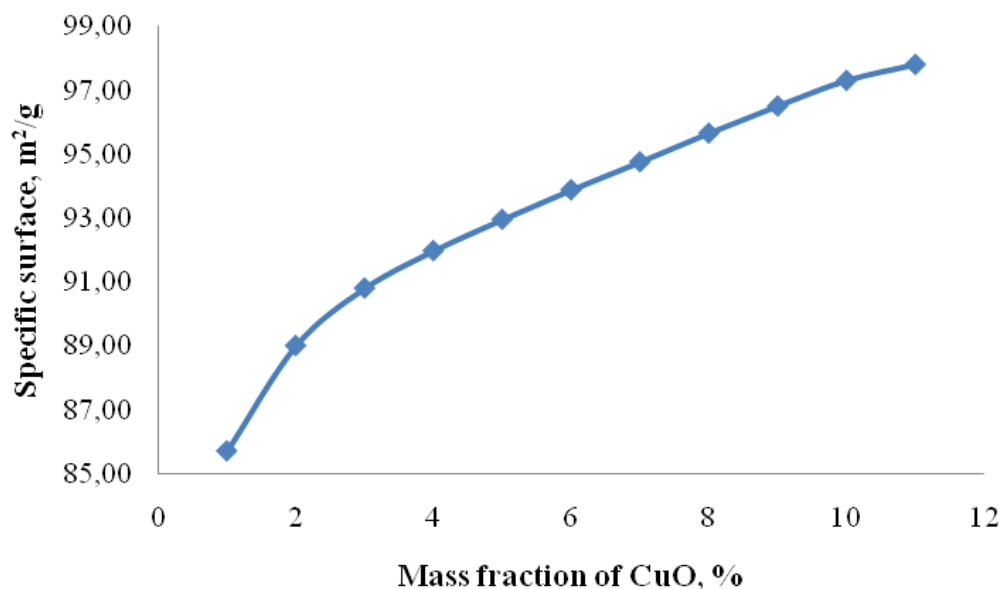

**Figure 2. Influence of CuO on the degree of increase in the specific surface area of the absorber.**

It can be seen that with an increase in the amount of CuO by the degree of increase in the specific surface of the absorber from 93.1 m²/g to 97.8 m²/g. Therefore, for further research, the amount of binding additives CuO 10% and MgO 7% was limited.

From the data obtained, it is possible to obtain an absorber with added CuO 10% and MgO 7% improves the physicochemical indicators for mechanical strength: the splitting strength index increases by 0.41 kg/mm and the specific surface area is 97.8 m<sup>2</sup>/g.

## REFERENCES

1. Sh.Kh.Tavashov, A.T.Dadakhodjaev, Kh.Ch.Mirzakulov "Technology development production of a zinc oxide scavenger" // ACADEMICIA: an international multidisciplinary research journal // India, ISSN: 2249-7137 Vol. 10, Issue 4, April 2020-714 p.
2. Sh.Kh.Tavashov, A.T.Dadakhodjaev, Kh.Ch.Mirzakulov "Recycling of zinc oxide scavengers" // AJMR: asian journal of multidimensional research // India, ISSN: 2278-4853 Vol 9, Issue 3, March, 2020-152 p.
3. Tavashov Sh.Kh., Farmanov B.I., Mirzakulov Kh.Ch., Dadahodzhaev A.T. "Nitric acid dissolution of the spent absorber of sulfur compounds giap - 10", Proceedings of the Republican scientific-technical conference "Innovative technologies based on local raw materials and secondary resources", Volume 2, April 19-20, Urgench-2021
4. Sh.Kh.Tavashov, Kh.Ch. Mirzakulov, AT Dadakhodjaev "Absorbers of sulfur compounds from spent catalysts", Chemical technology and equipment materials of reports of the 84th scientific and technical conference dedicated to the 90th anniversary of BSTU and the Day of Belarusian Science (with international participation), Minsk 2020
5. A.T.Dadakhodzhaev, Sh.Kh. Tavashov "The choice of the method of processing spent GIAP - 10 in zinc white" // Collection of articles of the republican scientific-practical conference "The role of innovative technologies in solving current problems of industry and agriculture" .// Karshi - 2019. 53 p.
6. A.T.Dadakhodjaev "Method of obtaining an absorbent substance for cleaning gases from sulfur compounds", Patent No. IAP 03269, Res. Uzbekistan - 2004.